

Pulse-shape discrimination with PbWO_4 crystal scintillators

L. Bardelli ^a, M. Bini ^a, P.G. Bizzeti ^a, F.A. Danevich ^{b,1},
T.F. Fazzini ^a, V.V. Kobychiev ^b, N. Krutyak ^c, P.R. Maurenzig ^a,
V.M. Mokina ^b, S.S. Nagorny ^b, M. Pashkovskii ^d, D.V. Poda ^b,
V.I. Tretyak ^b, S.S. Yurchenko ^b

^a*Dipartimento di Fisica, Università di Firenze and INFN, 50019 Firenze, Italy*

^b*Institute for Nuclear Research, MSP 03680 Kyiv, Ukraine*

^c*Skobeltsyn Institute of Nuclear Physics, M.V. Lomonosov Moscow State University, Vorob'evy Gory, 119992, Moscow, Russia*

^d*Department of Semiconductors Physics, Ivan Franko National University, UA-79005 Lviv, Ukraine*

Abstract

The light output, α/β ratio, and pulse shape have been investigated at -25°C with PbWO_4 crystal scintillators undoped, and doped by F, Eu, Mo, Gd and S. The fast $0.01 - 0.06\ \mu\text{s}$ and middle $0.1 - 0.5\ \mu\text{s}$ components of scintillation decay were observed for all the samples. Slow components of scintillation signal with the decay times $1 - 3\ \mu\text{s}$ and $13 - 28\ \mu\text{s}$ with the total intensity up to $\approx 50\%$ have been recognized for several samples doped by Molybdenum. We found some indications of a pulse-shape discrimination between α particles and γ quanta with PbWO_4 (Mo doped) crystal scintillators.

Key words: Scintillation detector, PbWO_4 crystals, Doping, Pulse-shape discrimination

PACS: 29.40.Mc

¹ Corresponding author. Address: Institute for Nuclear Research, Prospect Nauki 47, MSP 03680 Kyiv, Ukraine; tel: +380-44-525-1111; fax: +380-44-525-4463; e-mail address: danevich@kinr.kiev.ua

1 Introduction

Lead tungstate crystals (PbWO_4) are discussed in [1] as promising material for a high sensitivity experiment to search for double beta decay of ^{116}Cd with the help of cadmium tungstate crystal scintillators (CdWO_4). PbWO_4 crystals can be used as light-guides and high efficiency active shield for low-background CdWO_4 scintillation detectors. Using of radiopure PbWO_4 scintillators could allow to build a 2β experiment to search for $0\nu 2\beta$ decay of ^{116}Cd at the level of sensitivity $T_{1/2}^{0\nu 2\beta} \sim 10^{26}$ yr, which corresponds to the Majorana neutrino mass $\sim 0.1 - 0.05$ eV.

As it has been demonstrated (see, for instance [2,3,4]), a pulse-shape discrimination ability of the scintillation detector is important to interpret and to reject background caused by internal contamination of ^{232}Th and ^{238}U daughters. However, pulse-shape discrimination technique can be also useful to suppress background in a detector from internal contamination in surrounding scintillator (for instance, γ background in the CdWO_4 detector from U/Th contamination in the PbWO_4 surrounding crystals [1]). Pulse-shape discrimination in PbWO_4 scintillators can be useful to suppress background γ events in CdWO_4 detector from ^{208}Tl decays in PbWO_4 by off line tagging α events from the preceding ^{212}Bi decay. Similarly the γ events from ^{214}Bi β decay can be rejected by tagging subsequent ^{214}Po α events in PbWO_4 scintillators.

The aim of the present study was to check a possibility of pulse-shape discrimination with PbWO_4 crystal scintillators. In addition, the influence of Fluorine doping on light yield of PbWO_4 scintillators reported in [5] has been checked, and response of crystals with different dopants to α particles has been investigated.

2 Measurements and results

2.1 Samples

PbWO_4 single crystals were grown using Czochralski technique in an inert (Argon) atmosphere. Dopants (RE_{3+} ions) were added to the raw material ($\text{PbO} + \text{WO}_3$) in the form of RE_2O_3 oxides. Fluorine, molybdenum and sulfur were in the melt as a PbF_2 , MoO_3 and PbSO_4 , correspondingly. Samples for measurements were cut from crystal boules and polished in the form of plates with a diameter of 10 – 15 mm and a thickness of ≈ 5 mm. The PbWO_4 crystals used in the present research are listed in the Table 1. All the crystals were colorless and transparent except one (6/03), which was slightly yellow

colored. Some of the samples have visible core-like defects. Concentration of Mo, Eu, Gd dopant elements was checked by mass-spectrometry with the help of a secondary ion mass spectrometer (Cameca, IMS-4F). The results of the mass-spectrometry qualitatively confirm the concentration of the dopant elements known from the growth conditions.

Table 1

Parameters of the PbWO_4 samples.

Sample	Dopants	Concentration in the melt (ppm)
20/01	—	—
6/03	F	400
8/03	F	4000
9/03	F, Gd	2000, 1000
7/03	F, Eu	400, 100
13/03	F, Eu	2000, 20
10/03	F, Gd, Mo	1700, 90, 15800
11/03	F, Gd, Mo	1000, 50, 30000
12/03	F, Gd, Mo	870, 40, 78800
14/03	F, Eu, Mo	1000, 6, 30000
15/03	F, Eu, Mo, S	820, 5, 24500, 1000

2.2 Relative light output

The samples of PbWO_4 scintillators were wrapped by PTFE reflector tape and optically connected to the PMT EMI9256KB by Dow Corning Q2-3067 optical couplant. The detector was placed into temperature controlled chamber, where the temperature of the detector was stabilized and measured with an accuracy of $\pm 1^\circ \text{C}$. The shaping time of the ORTEC (Model 572) amplifier was set to $0.5 \mu\text{s}$. The relative light output of the PbWO_4 detectors was measured at -25°C with ^{60}Co and ^{137}Cs γ sources.

Fig. 1(a) shows the energy spectra of ^{57}Co and ^{137}Cs γ sources measured with the crystal PbWO_4 doped by F, Gd and Mo (10/03). An energy resolution $\text{FWHM} = 23\%$ was obtained for 662 keV γ line of ^{137}Cs .

The spectrum measured with ^{241}Am α source is shown in Fig. 1(b). It should be stressed that even the 60 keV γ peak of ^{241}Am is still resolved from the PMT noise. The energy resolution for the 60 keV γ peak is $\text{FWHM} \approx 87\%$.

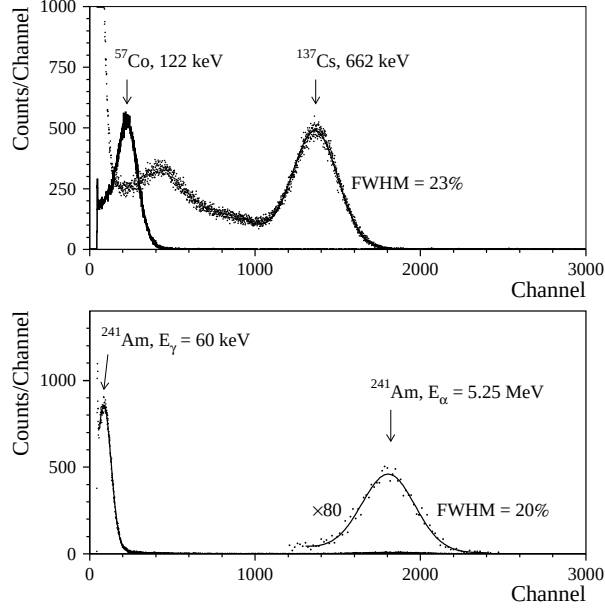


Fig. 1. Energy spectra measured by the $\text{PbWO}_4(\text{F,Gd,Mo})$ scintillation crystal (10/03) with (a) ^{57}Co and ^{137}Cs sources, and (b) ^{241}Am source at -25°C .

The samples of PbWO_4 scintillators were prepared from crystal boules of different diameter (10 – 15 mm) and have values of height-to-diameter ratio (h/D) in the range 0.3 – 0.5. Relative light output of scintillators with the high index of refraction (the index of refraction of PbWO_4 crystals is 2.2) depends on the h/D ratio. To take into account such an effect, we have carried out measurements with CdWO_4 crystal scintillators (index of refraction in the range 2.1 – 2.3) with the h/D ratio in the range 0.06 – 0.9. A CdWO_4 crystal with the initial value of $h/D = 0.9$ was used for the measurements. To obtain the samples with lower h/D ratio, the crystal was cut on the cleavage plane. The CdWO_4 scintillators were covered by teflon reflector and optically coupled to Philips XP2412 photomultiplier. The measurements were carried out with a ^{207}Bi gamma source. The results of measurements are shown on Fig. 2. The data were fitted by the polynomial function $f(h/D) = p_0 + p_1 \cdot (h/D) + p_2/(h/D)$. Then the values of relative light output measured with PbWO_4 scintillators were corrected by using the experimentally determined coefficients. The relative light output measured with the PbWO_4 samples after correction on the height-to-diameter ratio (corrections do not exceed 10%) are presented in Table 2.

We do not observe an increasing of light output of PbWO_4 scintillators grown by Czochralski method and doped by Fluorine, as reported in [5]. This result is in agreement with [6]. Recently a factor of 2.5 increase of the light yield was reported for F doped PbWO_4 crystals grown by Bridgman method [7]. In opinion of authors of Ref. [7] "F-ion does not enter substantially in Czochralski-grown PWO, and any improvement has not been observed". Therefore, additional investigations are necessary to understand how the growth methods affect the

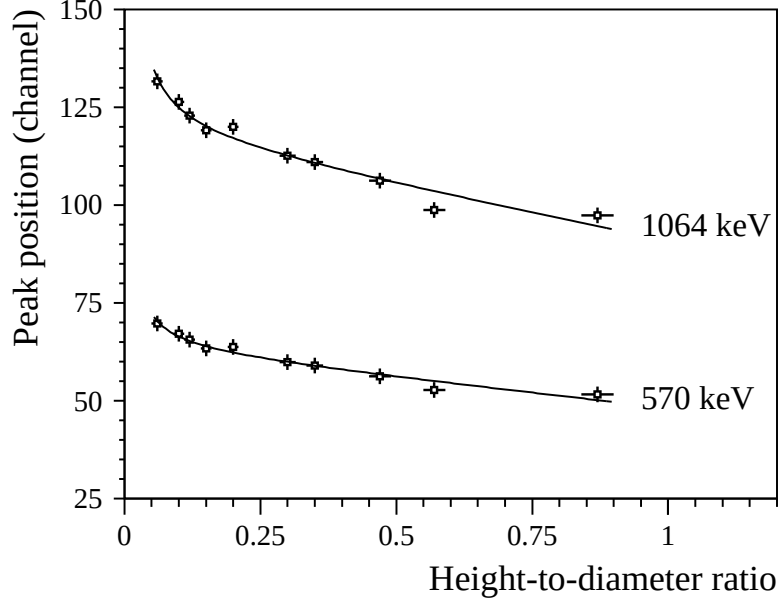


Fig. 2. Dependence of relative pulse amplitude on sample height-to-diameter ratio measured with CdWO_4 crystal scintillator. The solid line represents the fits of the data by polynomial function.

properties of PbWO_4 crystals. It should be stressed that only initial concentrations of the dopants in the raw materials were known in all cases. A careful quantitative control of dopant elements, as well as impurities concentrations in the crystals are required for such investigations.

2.3 α/β ratio

The α/β ratio was measured with the help of the collimated α particles of a ^{241}Am source. As it was checked by surface-barrier silicon detector, the energy of α particles was reduced to about 5.25 MeV going through 2 mm of air in the collimator. The energy scale was calibrated with the help of the 570 and 1064 keV γ lines of a ^{207}Bi source. The results are presented in Table 2. The α/β ratio measured with the external α source are in the range of 0.20–0.32 which is an agreement with result reported in [1]. The errors of the α/β ratio are mainly due to uncertainties in the energy calibration of the PbWO_4 detectors due to the poor energy resolution of the γ peaks.

In addition, the α peak of ^{210}Po from internal contamination of crystals by ^{210}Pb was used to measure the α/β ratio. The energy spectrum of PbWO_4 scintillator (sample 10/03) measured during 2600 s is presented in Fig. 3. A clear peak in the spectrum can be attributed to α decay of ^{210}Po (the energy of α particles is 5.31 MeV) from internal contamination of the crystal by ^{210}Pb . The α/β ratio is 0.29 ± 0.03 , the activity of ^{210}Po in the crystal is 24 ± 2

Bq/kg.

As one can see in Table 2, the values obtained with external α source and by using the peak of internal ^{210}Po are in agreement. Some difference in the values of the α/β ratio between the studied PbWO_4 samples was observed. However, we can not interpret the difference as own properties of the samples. It is because the α/β ratio is not only a property of a crystal, but also a certain characteristics of the scintillation detector depending on the shape, sizes, surface treatment, transparency of a crystal, etc. To check a possible effect of dopant elements on the α/β ratio in PbWO_4 scintillators, one has to provide the same shape, sizes, transparency (without visible defects) and surface quality of samples.

2.4 Pulse-shape discrimination for γ quanta and α particles

2.4.1 Shapes of scintillation light pulses

The shapes of scintillation light pulses in the PbWO_4 crystals were studied for α particles from ^{241}Am source and for γ quanta from ^{137}Cs and ^{60}Co sources with the help of the 125 MSample/s 12 bit digitizer described in [8]. The shapes of scintillation pulses in the sample 13/03, and in the samples doped by Molybdenum were also measured in a time interval $\approx 50 \mu\text{s}$ with the help of the

Table 2

Relative light output and α/β ratio measured with an external ^{241}Am α source, and by using the α peak of ^{210}Po from internal contamination of the PbWO_4 samples.

Sample, dopants	Relative light output	α/β ratio	
		external α source	^{210}Po
20/01 (undoped)	1.00	0.24(3)	0.22(3)
6/03 (F)	0.94	0.21(3)	0.21(3)
8/03 (F)	0.98	0.22(3)	0.20(3)
9/03 (F,Gd)	0.81	0.26(4)	0.25(4)
7/03 (F,Eu)	0.73	0.19(4)	—
13/03 (F,Eu)	0.92	0.22(3)	0.21(3)
10/03 (F,Gd,Mo)	2.98	0.32(3)	0.29(3)
11/03 (F,Gd,Mo)	1.92	0.23(3)	0.22(3)
12/03 (F,Gd,Mo)	1.35	0.21(3)	0.22(3)
14/03 (F,Eu,Mo)	1.83	0.23(3)	0.22(3)
15/03 (F,Eu,Mo,S)	1.73	0.21(3)	0.22(3)

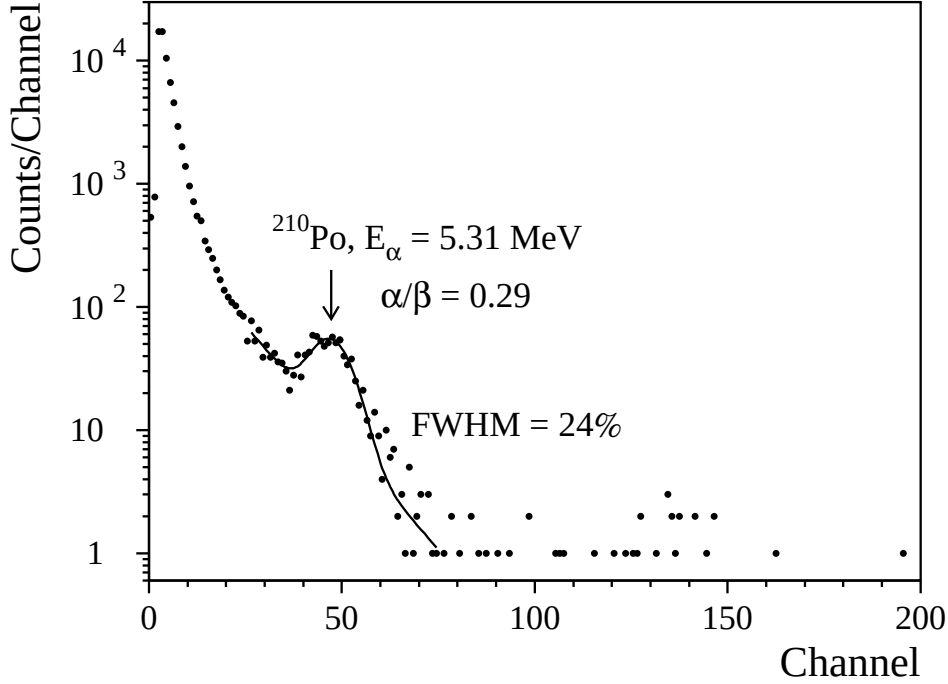


Fig. 3. Energy spectrum of PbWO₄ scintillation crystal (10/03) measured during 2600 s. The clear peak in the spectrum at the energy ≈ 1.54 MeV (in γ scale) can be attributed to α decay of ^{210}Po from internal contamination of the crystal by ^{210}Pb . The α/β ratio is 0.29.

20 MSample/s 12 bit digitizer [9]. To determine shapes of scintillation pulses for the sample 13/03, and for the samples with Molybdenum, the data obtained with both the 20 and 125 MSample/s digitizers were used. The pulse shapes were constructed in the time interval $0 - 1.5 \mu\text{s}$ from the 125 MSample/s data, and in the interval $1.5 - 50 \mu\text{s}$ from the data measured by the 20 MSample/s device. The pulse shapes for γ quanta and α particles measured with the PbWO₄ crystal (7/03) doped by F and Eu, and (14/03) doped by F, Eu, Mo are depicted in Fig. 4. The pulse shape can be fitted by a sum of exponential functions:

$$f(t) = \sum A_i (e^{-t/\tau_i} - e^{-t/\tau_0}) / (\tau_i - \tau_0), \quad t > 0,$$

where A_i are intensities, and τ_i are decay constants for different light emission components, τ_0 is the integration constant of electronics ($\approx 0.02 \mu\text{s}$). The values of A_i and τ_i obtained by fitting the average of a few thousand individual α and γ pulses are presented in Table 3.

The $0.01 - 0.06 \mu\text{s}$ and $0.1 - 0.5 \mu\text{s}$ decay components are in agreement with the results obtained in [10,11,12,13,14,15,16,17]. The slow $1 - 3 \mu\text{s}$ decay of PbWO₄ scintillation was also observed in [11,12,18], while $13 - 28 \mu\text{s}$ decay components were never reported for PbWO₄ scintillators. We were not able to measure the nanosecond ($\approx 1 - 9 \text{ ns}$) decay component, because of a comparatively large

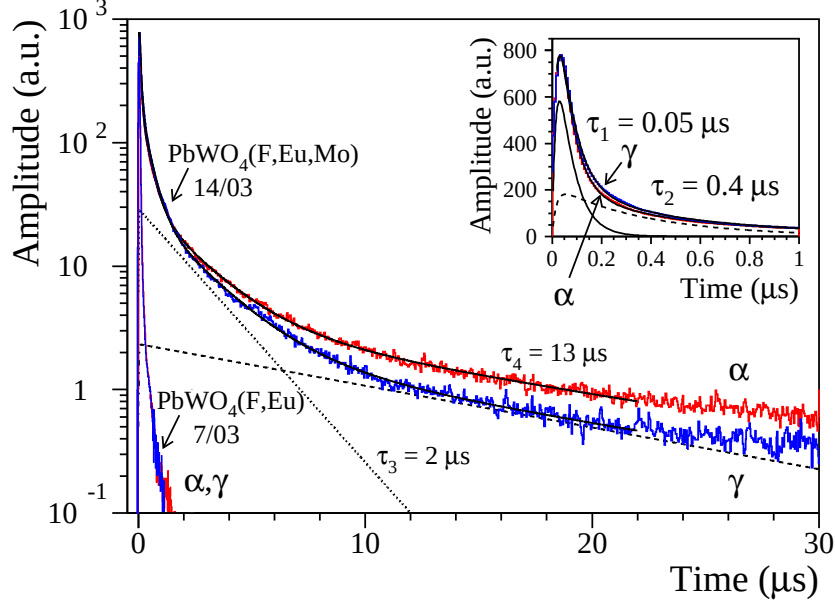


Fig. 4. Decay of scintillation of the PbWO_4 crystal (14/03, doped by F, Eu, Mo) for γ quanta and α particles and their fit by four components. Pulse shapes of PbWO_4 scintillator doped by F and Eu (7/03) are shown for comparison. (Inset) The first part of the PbWO_4 (14/03) α and γ pulses.

value of integration constant of the electronics $\approx 0.02 \mu\text{s}$ used in the present study.

2.4.2 Pulse-shape discrimination by optimal filter method

A small difference in light pulse shapes could allow to discriminate $\gamma(\beta)$ events from α particles. We applied for this purpose two approaches: the optimal filter technique proposed in [19] and developed in [9] for CdWO_4 crystal scintillator, and the mean time method.

To obtain a numerical parameter for the PbWO_4 signal, the so-called shape indicator (SI), the following formula was applied for each pulse:

$$SI = \sum f(t_k)P(t_k) / \sum f(t_k),$$

where the sum is over time channels k , starting from the origin of the pulse up to certain time, $f(t_k)$ is the digitized amplitude (at the time t_k) of a given signal. The weight function $P(t)$ is defined as: $P(t) = \{f_\alpha(t) - f_\gamma(t)\} / \{f_\alpha(t) + f_\gamma(t)\}$, where $f_\alpha(t)$ and $f_\gamma(t)$ are the reference pulse shapes for α particles and γ quanta. Reasonable discrimination between α particles and γ quanta was achieved with Molybdenum doped PbWO_4 crystals as one can see in Fig. 5 where the shape indicator distributions measured by the $\text{PbWO}_4(\text{F,Gd,Mo})$ scintillation crystal (10/03) with α particles ($\approx 5 \text{ MeV}$) and γ quanta ($\approx 1.3 \text{ MeV}$) are shown. The small tail in the shape indicator distribution for γ at

Table 3

The time properties of PbWO_4 crystal scintillators. The decay constants and their intensities (in percentage of the total intensity) for γ quanta and α particles are denoted as τ_i and A_i , respectively. The factor of merit for pulse-shape discrimination (FOM , see text) characterizes the efficiency of pulse-shape discrimination with the help of the optimal filter (OF), and mean time (MT) methods.

Sample, dopants	Type of irradiation	Decay constants (μs) and relative intensities				FOM	
		τ_1 (A_1)	τ_2 (A_2)	τ_3 (A_3)	τ_4 (A_4)	OF	MT
20/01 (undoped)	γ	0.016 (72%)	0.24 (17%)	2.6 (11%)	–	0.05	0.02
	α	0.016 (74%)	0.22 (16%)	1.9 (11%)	–		
6/03 (F)	γ	0.012 (77%)	0.29 (12%)	1.1 (11%)	–	0.08	0.06
	α	0.013 (78%)	0.24 (11%)	1.0 (11%)	–		
9/03 (F,Gd)	γ	0.026 (86%)	0.13 (14%)	1–5 (< 0.5%)	–	0.03	0.01
	α	0.031 (84%)	0.15 (16%)	1–5 (< 0.5%)	–		
7/03 (F,Eu)	γ	0.014 (95%)	0.24 (5%)	1–5 (< 0.5%)	–	0.04	0.01
	α	0.016 (94%)	0.19 (6%)	1–5 (< 0.5%)	–		
13/03 (F,Eu)	γ	0.026 (79%)	0.5 (13%)	2.0 (7%)	≈ 17 (1%)	0.48	0.35
	α	0.028 (84%)	0.4 (10%)	1.8 (5%)	≈ 18 (1%)		
10/03 (F,Gd,Mo)	γ	0.064 (42%)	0.30 (46%)	2.3 (8%)	20 (4%)	2.4	1.6
	α	0.061 (33%)	0.37 (40%)	2.6 (14%)	28 (12%)		
11/03 (F,Gd,Mo)	γ	0.059 (25%)	0.40 (32%)	2.5 (24%)	16 (19%)	0.96	0.96
	α	0.047 (23%)	0.36 (26%)	2.1 (25%)	15 (26%)		
12/03 (F,Gd,Mo)	γ	0.058 (25%)	0.38 (27%)	2.4 (24%)	17 (24%)	1.5	1.4
	α	0.048 (22%)	0.35 (23%)	2.1 (23%)	16 (32%)		
14/03 (F,Eu,Mo)	γ	0.062 (25%)	0.38 (35%)	2.1 (27%)	13 (13%)	2.3	1.5
	α	0.054 (24%)	0.35 (28%)	2.0 (27%)	13 (21%)		
15/03 (F,Eu,Mo,S)	γ	0.064 (26%)	0.38 (34%)	2.1 (27%)	14 (12%)	1.6	1.4
	α	0.054 (25%)	0.34 (28%)	1.7 (27%)	13 (20%)		

≈ 50 can be explained by background α events from ^{210}Po inside the crystal (see subsection 2.3 and Fig. 3).

As a measure of discrimination ability (factor of merit, FOM), the following formula can be used:

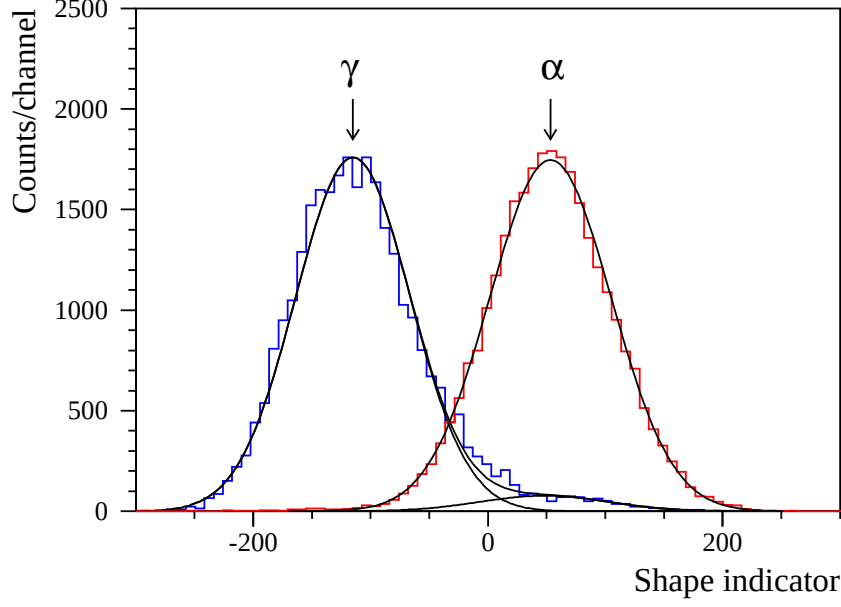


Fig. 5. Distributions of the shape indicator (see text) for pulses produced by γ quanta and α particles in $\text{PbWO}_4(\text{F,Gd,Mo})$ scintillation crystal (10/03). The small tail in the shape indicator distribution for γ at ≈ 50 can be explained by background α events from ^{210}Po inside the crystal.

$$FOM = |SI_\alpha - SI_\gamma| / \sqrt{\sigma_\alpha^2 + \sigma_\gamma^2},$$

where SI_α and SI_γ are mean SI values for α particles and γ quanta distributions (which are well described by Gaussian functions), σ_α and σ_γ the corresponding standard deviations. For the distributions presented in Fig. 5, the factor of merit is $FOM = 2.4$.

2.4.3 Mean time method

The data were processed also by using the mean time method. The following formula was applied to calculate the parameter $\langle t \rangle$ (mean time) for each pulse:

$$\langle t \rangle = \sum f(t_k)t_k / \sum f(t_k),$$

where the sum is over time channels k , starting from the origin of pulse and up to a certain time. The distributions of parameters $\langle t \rangle$ are well described by Gaussian functions. Therefore the factor of merit FOM can be used to characterize efficiency of pulse-shape discrimination. As one can see from Table 3, the optimal filter method provides slightly better pulse-shape discrimination. At the same time the mean time method is easy to apply because it does not need the construction of a weight function.

3 Conclusions

The light output, α/β ratio, and pulse shape have been investigated at -25°C with PbWO_4 crystal scintillators undoped, and doped by F, Eu, Mo, Gd and S. Doping of PbWO_4 crystals by Molybdenum improves light output by approximately a factor of 1.5–3. This result is an agreement with data published before [20,21]. The relative light output of Europium doped PbWO_4 crystals is on the level of 0.7 – 0.9 relatively to undoped sample. We do not observe an increase of light output by Fluorine doping as reported in [5] and [7]. This fact can be explained by different methods used to grow $\text{PbWO}_4(\text{F})$ crystals: Bridgman in [5,7], and Czochralski in the present study and in the work [6] where the effect was not observed too.

Values of the α/β ratio measured with different PbWO_4 samples vary in the range of 0.20 – 0.32. However, such a difference can be explained by unequal quality of the samples that have been used in the measurements. To study the possible effect of doping on the α/β ratio one should prepare the samples with the same sizes, surface quality, and without visible defects.

Fast 0.01 – 0.06 μs and middle 0.1 – 0.5 μs components of scintillation decay were observed for all the samples. Slow components of scintillation signal with the decay times 1 – 3 μs , and 13 – 28 μs with the total intensity at the level of $\approx 45 - 50\%$ have been measured for samples doped by Molybdenum. The undoped crystal as well as crystals without Molybdenum have shown a lower intensity of the slow components at the level of $\leq 0.5 - 10\%$.

We found some indications of a pulse-shape discrimination between α particles and γ quanta by applying the mean time and optimal filter methods. The best discrimination was achieved with PbWO_4 crystals doped by Molybdenum.

References

- [1] F.A. Danevich et al., Nucl. Instr. Meth. A 556 (2006) 259.
- [2] F.A. Danevich et al., Phys. Rev. C 68 (2003) 035501.
- [3] Yu.G. Zdesenko et al., Astropart. Phys. 23 (2005) 249.
- [4] P. Belli et al., Nucl. Instr. Meth. A 498 (2003) 352.
- [5] X. Liu et al., Phys. Status Solidi A 190 (2002) R1.
- [6] M. Kobayashi et al., Nucl. Instr. Meth. A 540 (2005) 381.
- [7] Chongzhi Ye et al., Nucl. Instr. Meth. A 566 (2006) 757.

- [8] G. Pasquali et al., Nucl. Instr. Meth. A. 570 (2007) 126.
- [9] T. Fazzini et al., Nucl. Instr. Meth. A 410 (1998) 213.
- [10] J.A. Groenink and G. Blasse, J. Solid State Chem. 32 (1980) 9.
- [11] A.N. Belsky et al., Chem. Phys. Lett. 243 (1995) 552.
- [12] R.Y. Zhu et al., Nucl. Instr. Meth. A 376 (1996) 319.
- [13] M. Kobayashi et al., Nucl. Instr. Meth. A 399 (1997) 261.
- [14] A.N. Annenkov et al., Nucl. Instr. Meth. A 403 (1998) 302.
- [15] Jianru Han et al., Prog. Cryst. Growth Charact. Mater. 40 (2000) 167.
- [16] M. Kobayashi et al., Nucl. Instr. Meth. A 465 (2001) 428.
- [17] Yu. Zorenko et al., Radiat. Meas. 38 (2004) 397.
- [18] D. Millers et al., Radiat. Meas. 29 (1998) 263.
- [19] E. Gatti and F. De Martini, Nuclear Electronics 2, IAEA, Vienna, 1962, p. 265.
- [20] A. Annenkov et al., Nucl. Instr. Meth. A 450 (2000) 71.
- [21] M. Kobayashi et al., Nucl. Instr. Meth. A 486 (2002) 170.